



Buzzi Unicem Next is the name of a family of hydraulic binders based on sulfoaluminate clinker, which is obtained by burning a mixture of bauxite, gypsum and limestone at a temperature of approximately 1,350°C and subsequently ground.

Next base is formulated with the optimal proportions of **Next clinker** and anhydride for most applications.

Next base ensures consistent performances over time and excellent storage stability in the products in which it is used.

Next base can be used as a rapid binder or in combination with Portland cement to produce products characterized by low shrinkage and rapid development of strength after a short curing time.

Next base can be used to formulate products for a wide range of applications due to its compatibility with all types of setregulating admixtures, superplasticizers, viscosifiers, expansive agents, accelerators, retarders, etc.

Next base confers exceptional durability, low permeability to aggressive substances and very high resistance to sulfates to the products in which it is used.

Buzzi Unicem Next base SR03 Hydraulic binder based on sulfoaluminate clinker



“German Technical Approval Z - 3.15 - 2130” issued by Deutsches Institut für Bautechnik (DIBt)

Properties

Next base SR03 is classified as a hydraulic binder that is highly resistant to sulfates.

Main chemical ingredients

CaO	41 – 45%
Al ₂ O ₃	22 – 26%
SiO ₂	8 – 9%
SO ₃	17 – 19%
Cl ⁻	< 0,1%
Cr VI	< 2,0 ppm

Main ingredients of the hydraulic binder

Clinker CSA	(81 ± 5)%
CaSO ₄	(19 ± 5)%

Calcium sulfoaluminate content


C ₄ A ₃ S̄	(45 ± 5)%
----------------------------------	-----------

Density	2.800 kg/m ³
Blaine specific surface area UNI EN 196-6]	> 4.000 cm ² /g
Color	light gray
Initial set time [UNI EN 196/3]	< 20 min
Water requirement	33 ± 2%

Average compressive strength

In compliance with UNI EN 196-1

Time	[MPa]
3 hours	> 20
8 hours	> 30
28 days	> 42,5

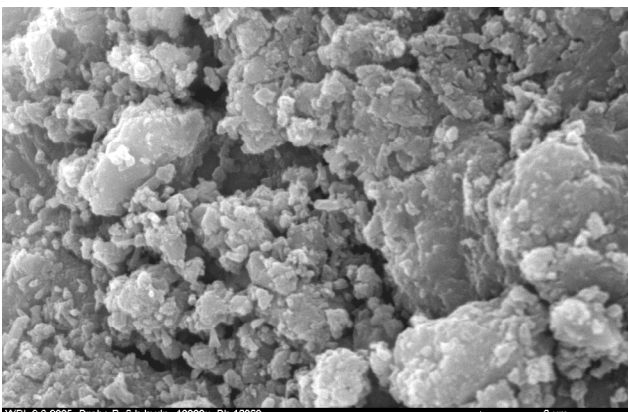

WDI, 2.9.2005, Probe B, 6 h hydr., 10000x, Ph.13060

Applications

Next base can be used alone or in combination with Portland cement for a large number of applications in the premix and precast sectors.

- Adhesives and technical mortars
- Rapid hardening, premixed plasters, mortars and grouts
- Premixed plasters, mortars and grouts for use at low temperatures
- Premixed mortars and grouts with low permeability and high resistance to sulfates
- Premixed, bagged mortars and grouts whose performance remains intact after the bag has been open for a longer period of time than the same products prepared with aluminous cements
- Sprayable or injectable products
- Precast structural and non-structural components requiring rapid removal of formwork
- Precast components of any color
- Precast components with high resistance to sulfates and freezing-thawing cycles

Warnings

- When designing different formulations of ternary binders, we recommend that the **Next base** - Portland cement components remain within the 40%-60% (in weight) range of the total binder.
- The set times and speed of strength development can be customized by varying the retardant admixture (citric or tartaric acid) and the accelerant admixture (lithium carbonate).
- If **Next base** is used as a set accelerator for Portland cements, we recommend that it comprises between 10%- 20% of the total binder

- We recommend against using Next base in the preparation of materials that will be exposed to extremely high temperatures such as firebrick or mortars used in kiln or similar construction.
- Next base is supplied in bulk, 25 kg bags or big-bags.
- Please see the Buzzi Unicem Next user manual for further information.
- The safety sheet can be downloaded from the website: www.buzziunicem.it.

CSA-based product line

Next base

Binder based on calcium sulfoaluminate and anhydride designed for formulating products characterized by low shrinkage and rapid development of mechanical strength.

Next binder

Ready-to-use ternary binder (consisting of a combination of sulfoaluminate clinker, anhydride and Portland cement) for applications in the precast, premix and readymix concrete sectors where rapid development of strength, low shrinkage and rapid drying are necessary.



Environmental sustainability

Because of the low carbon and calcium content in the raw materials, the production cycle of Next formulations reduces the CO₂ emissions into the atmosphere.

Nota: *The instructions provided above are the result of our best experience and are for indicative purposes only. We cannot be held liable for any defect or damaged caused by the improper use of the product or if it is not used under the recommended conditions. Our Technical Assistance Department is available to provide further advice on the correct use of the product and to conduct technical tests.*

Buzzi Unicem S.r.l.

via Luigi Buzzi, 6
15033 Casale Monferrato [AL]
Italy
tel +39 0142 416219
fax +39 0142 416320
direzionecommerciale@buzziunicem.it
www.buzziunicem.it